

# Anhui Sentai WPC TEC Flooring Co., Ltd.

## TEST REPORT

**SCOPE OF WORK**

SPC Flooring/rigid vinyl plank

**REPORT NUMBER**

190801008SHF-003

**TEST DATE(S)**

2019-08-01 - 2019-08-28

**ISSUE DATE**

2019-08-28

**PAGES**


5

**DOCUMENT CONTROL NUMBER**

LFT-APAC-SHF-OP-10k(May 1, 2019)

© 2019 INTERTEK

Intertek Testing Services Shenzhen Ltd. Shanghai Fengxian Branch

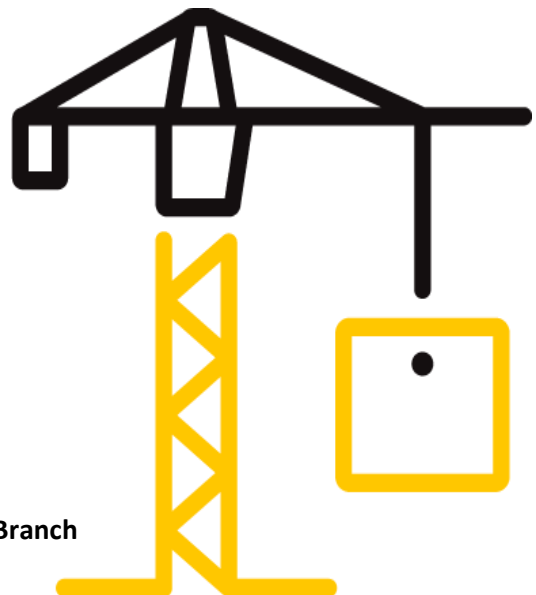

## Test Report

### Statement

- 1.This report is invalid without company's special seal for testing on assigned page.
- 2.This report is invalid without authorized person's signature.
- 3.This report is invalid where any unauthorized modification indicated.
- 4.Don't copy this report in partial (except full copy) without any official approval in written by our company. This report is invalid without re-stamping the special seal for testing in copying report.
- 5.Any holder of this document is advised that this report is for the exclusive use of Intertek's Customer and is provided pursuant to the agreement between Intertek and its Customer. Intertek's responsibility and liability are limited to the terms and conditions of the agreement. This report was made with due care within the limitation of a defined scope of work and on the basis of information, materials and instructions received from the Customer or its nominated third parties. Intertek is under no obligation to refer to or report upon any facts or circumstances which are outside the specific instructions received and accepts no responsibility to any parties whatsoever, following the issue of the report, for any matters arising outside the agreed scope of the works. The tests results are not intended to be a recommendation for any particular course of action. Customer is responsible for acting as it sees fit on the basis of such results.
- 6.Intertek's written consent is required to use Intertek's name or logo on the object, product or service being tested. The observations and test results in this report relate only to the sample under test. This report alone does not indicate that the item, product or service has passed any Intertek certification program.

# Test Report

Issue Date: 2019-08-28 Intertek Report No. 190801008SHF-003  
 Applicant: Anhui Sentai WPC TEC Flooring Co., Ltd.  
 Address: No.19, Guohua Rd., Guangde TED Zone, Guangde, Anhui, China  
 Attn: Jerry Liu  
 Test Type : Performance test, samples provided by the applicant.

### Product Information

<b>Product Name</b>	SPC Flooring/rigid vinyl plank		<b>Brand</b>	/
<b>Sample Description</b>	Good Condition		<b>Sample Amount</b>	56 pieces
			<b>Received Date</b>	2019-08-14
<b>Sample ID</b>	<b>Model</b>	<b>Specification</b>		
S190801008SHF.005	SPC0335, 3.8/0.3mm	1220*181*3.8mm		

### Test Methods And Standards

<b>Test Standard</b>	ISO 4918:2016
<b>Specification Standard</b>	/
<b>Test Conclusion</b>	The samples were tested according to the above standards, and the results are shown in the following page.

Note:

- 1.This report relates specifically to the sample(s) that were drawn and provided by the applicant or their nominated third party. The reported result(s) provide no warranty or verification on the sample(s) representing any specific goods and/or shipment and only relate to the sample(s) as received and tested.
- 2.This report involved in 1220\*181\*3.8mm is issued solely based on the use of the data and information provided by the Customer. The Customer agrees that Intertek has no duty, responsibility or obligation to check accuracy or appropriateness or any other feature or aspect of the data and the information except to use and rely on them as provided and that Intertek shall not be held liable for the testing result or reliance on it by any party.

### Report Authorized


  
 Name: Sally Xie Name: Tod Qian  
 Title: Reviewer Title: Project Engineer

# Test Report

Issue Date: 2019-08-28

Intertek Report No. 190801008SHF-003

### Test Items, Method and Results:

Test Item: Castor chair test

Test Method: ISO 4918:2016

Conditioning: Condition the test specimens at (23 ± 2)°C and (50 ± 5)% relative humidity for at least 24h

Test Condition: At a temperature range of 18°C to 25 °C

- Load mass: 90 kg
- Test castors: Type W
- Speed of rotating platform: 20 r/min
- Speed of castor assembly: 50 r/min
- Total test revolutions: 25000 r
- Mounting of the specimen: Floating installation with click joints

### Test Result:

Type of damage	Observation (Yes/No)	Verdict
Delamination	No	Pass
Opening of joints	No	
Surface damage	No	
Crazing	No	
Maximum opening	0.02mm	No requirement Report the result
Maximum height differences	0.06mm	

### Test Photo:




After test

## Test Report


Issue Date: 2019-08-28

Intertek Report No. 190801008SHF-003

### Appendix A: Sample Received Photo

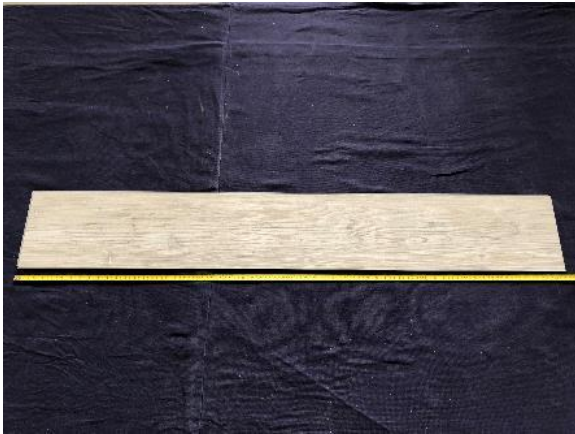

Front View(Test Face)

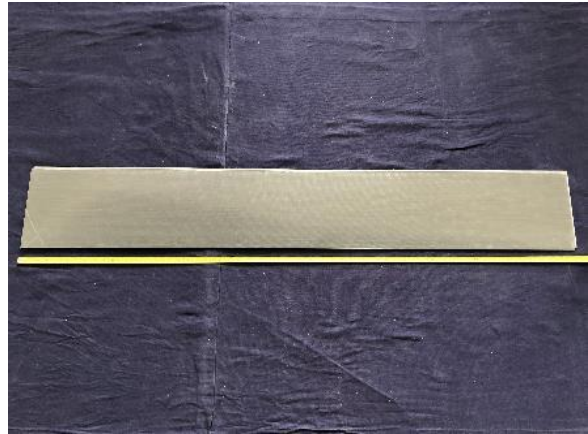

Back View

### Revision:

NO.	Date	Changes	Author	Reviewer
190801008SHF-003	2019-08-28	First issue	Tod Qian	Sally Xie